arXiv:1103.3429v1 [cond-mat.supr-con] 17 Mar 2011

Dissipation-driven superconductor-insulator transition in linear arrays of Josephson junctions capacitively coupled to metallic films

Alejandro M. Lobos and Thierry Giamarchi
DPMC-MaNEP, University of Geneva, 24 Quai Ernest-Ansermet CH-1211 Geneva, Switzerland.

(Dated: January 15, 2013)

We study the low-temperature properties of linear Josephson-junction arrays capacitively coupled to a proximate two-dimensional diffusive metal. Using bosonization techniques, we derive an effective model for the array and obtain its critical properties and phases at $T = 0$ using a renormalization group analysis and a variational approach. While static screening effects given by the presence of the metal can be absorbed in a renormalization of the parameters of the array, backscattering originated in the dynamically screened Coulomb interaction produces a non-trivial stabilization of the insulating groundstate and can drive a superconductor-insulator transition. We study the consequences for the transport properties in the low-temperature regime. In particular, we calculate the resisitivity as a function of the temperature and the parameters of the array, and obtain clear signatures of a superconductor-insulator transition that could be observed in experiments.

PACS numbers: 74.50.+r,74.40.Kb,74.25.F-

I. INTRODUCTION

Low-dimensional superconductors are systems displaying a surprisingly complex and rich physics, allowing the study of paradigmatical phenomena in condensed matter physics, like quantum phase transitions and quantum critical behavior, electronic localization, Coulomb blockade, etc.[1,2] In particular, an intriguing superconductor-insulator phase transition (SIT) was observed experimentally in superconducting films[3–5], wires[6–8], and in ultrasmall-capacitance Josephson junction arrays (JJAs) in two[9–11] and one dimensions[12–15], giving rise to an intense theoretical activity.[16,17] In this transition, as one of the parameters is varied (e.g., the normal-state resistance of the film, the thickness of the wire, the Josephson coupling E_J in the array, etc.) the groundstate of the system changes from superconducting to insulator.

In one-dimensional (1D) superconductors, one particular kind of excitation, the so-called quantum-phase slip (QPS) processes, have been recently the focus of an intense research.[8] The interest is based both on the putative role of QPS in the SIT in 1D[18], as well as for their potential uses in novel qubit architectures[19], a fact that has stimulated recent interesting experimental research in 1DJJAs.[20,21] A phase-slip is a discrete process occuring in a 1D superconductor, in which the amplitude of the order parameter vanishes temporarily at a particular point, allowing the phase of the order parameter to change abruptly in units of 2π. In particular, a QPS is a phase-slip excitation originated in macroscopic quantum tunneling of the phase of the order parameter.[22]

On the other hand, since the seminal works by Caldeira and Leggett[23], it has been known that dissipation in macroscopic quantum systems plays a central role. For instance, in a two-dimensional JJA capacitively coupled to a proximate two-dimensional electron gas (2DEG), Rimberg *et al.* observed a tunable-SIT upon variation of the backgate voltage V_g applied to the 2DEG.[10] In that work, it was shown that V_g has the effect of tuning the sheet resistance $R_\square$ in the 2DEG through the modulation of its electronic density, a fact that in turn modifies the electromagnetic environment of the JJA. It was argued later by Wagenblast *et al.*[24] that due to the incomplete screening of the Coulomb interaction provided by the 2DEG, the 2D plasma mode in the array is overdamped and the charging energy in the junction E_C is renormalized to higher values, producing a SIT whenever the ratio $E_J/\tilde{E}_C \sim 1$, with $\tilde{E}_C$ the renormalized E_C. While this scenario is reasonable in a 2D geometry, in a 1DJJA capacitively coupled to a 2DEG, the screening provided by the metal is typically very efficient, and a significant damping of the 1D propagating plasma mode is not expected.[25] This leads to the naive conclusion that in the 1DJJA/2DEG geometry, a dissipation-driven SIT should not occur. However, in a closely related Luttinger-liquid system placed in proximity to a metallic plane, a dissipation-driven quantum phase transition was predicted to occur.[26] This transition is driven by backscattering events originated in the Luttinger liquid under the effect of the dynamically screened Coulomb interaction. It is therefore interesting to study to what extent the same dissipative processes will affect the dynamics of QPS in 1D superconductors in proximity of a

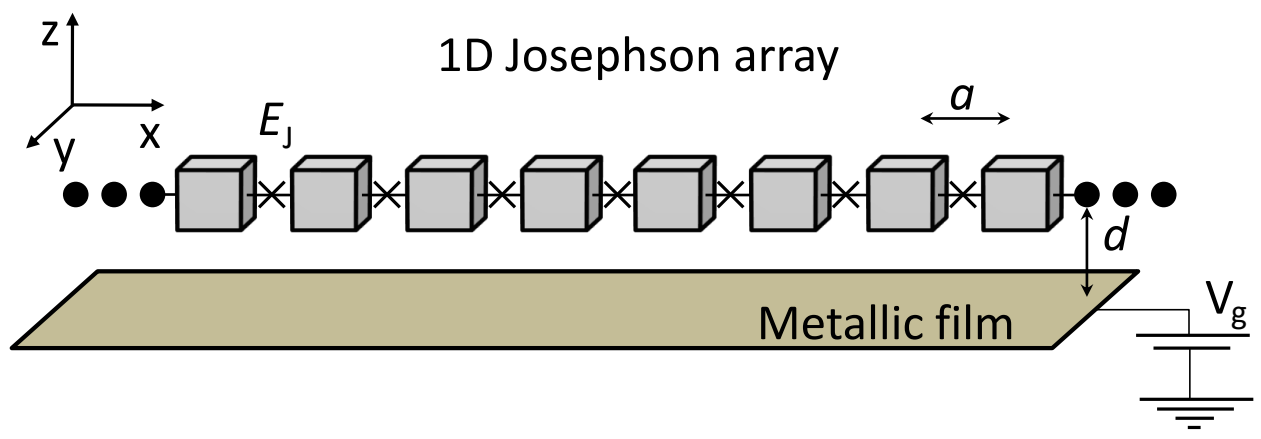

Figure 1: Scheme of the system under study. The 1DJJA is capacitively coupled to the metallic film, which controls the electromagnetic environment. A gate voltage allows to modify the sheet-resistance $R_\square$ of the film, modifying the dissipation in the 1DJJA.

diffusive metallic plane. Indeed, the question of dissipation in 1D superconductors is an active area of research, and theoretical predictions point towards the important role of intrinsic and/or extrinsic dissipation mechanisms in determining their $T = 0$ phase diagram.[27,28]

In this article we explore the possibility of a dissipation-driven SIT in a 1DJJA capacitively coupled to a proximate diffusive 2DEG. We concentrate in particular on the low-temperature phase diagram and on the transport properties of the array. Using a bosonization approach,[29] we derive the dissipative effective action from a microscopic Hamiltonian, and we elucidate the role of dissipation in the SIT. One important conclusion in our work is that for weak dissipation, the transition occurs always between a superconducting and an insulating phase, in contrast to other works predicting quadrupolar and normal phases.[27,28] We believe this is a consequence of a different kind of dissipation in the model. We find that, except in the experimentally challenging situation in which the Cooper-pair density in the superconducting islands is not commensurate, the SIT is always of the Berezinskii-Kosterlitz-Thouless (BKT) type,[30,31] and is originated in the unbinding of QPS/anti-QPS pairs. Dissipation stabilizes the insulating groundstate through the introduction of friction in the dynamics of the 1D superfluid density, a fact that could be observed experimentally in the dc-resistivity of the 1DJJA. Specifically, we predict a resistivity of the form $\varrho(T) \sim A_1 T^{\nu_1} + A_2 T^{\nu_2}$ in the superconducting phase, and $\varrho(T) \sim \eta T e^{\Delta/T}/\Delta$, in the insulating phase, with Δ the insulating gap and η the dissipation parameter.

The paper is organized as follows. In Section II we derive the effective model for a 1DJJA coupled to a 2DEG, in Section III we derive the $T = 0$ phase-diagram as a function of the parameters of the model, Section IV is devoted to the study of the experimental consequences of our results, and finally in Section V we present a summary and our conclusions.

II. MODEL

We start the analysis by considering an ideally isolated JJA, with length $L \to \infty$. To simplify the analysis, we neglect in the following the fermionic degrees of freedom forming the Cooper-pairs at a microscopic level. This "boson-only" approximation is belived to describe correctly the critical properties of a JJA at temperatures $T \ll T_c$, with T_c the superconducting critical temperature in the bulk of the superconducting island.[16] The usual description of the isolated, infinite 1DJJA is given in terms of the quantum phase model[2]

$$H_{\mathrm{JJA}} = \frac{1}{2}\sum_{i,j}\left(n_i - \bar{n}\right) v_{ij} \left(n_j - \bar{n}\right) + \sum_{\langle ij \rangle} E_J \left(1 - \cos\theta_i - \theta_j\right). \tag{1}$$

The dynamical variables of this model are the number of Cooper pairs n_i and the phase of the superconducting order parameter θ_i at every site i in the array. These variables obey the usual phase-number commutation relation in the BCS groundstate, i.e., $[\theta_i, n_j] = i\delta_{ij}$.[32] The first term in Eq. (1) represents the charging energy, with v_{ij} the unscreened Coulomb interaction [cf. Eq. (3)] between the excess charges at sites i and j, and $\bar{n}$ corresponds to an average charge imposed, e.g., by external gate voltages. The second term is the Josephson energy contribution, parametrized by E_J. In the following we use the convention $\hbar = k_B = 1$.

The critical properties of model Eq. (1) are more conveniently studied using a field-theoretical approach, valid for fluctuations of wavelengths much larger that the lattice parameter of the array a.[29] We therefore introduce the coarse-grained superfluid density $\delta\rho(x)$, defined as $\delta\rho(x_i) = (n_i - \bar{n})/a$, and we expand the Josephson term as $E_J \cos(\theta_i - \theta_j) \simeq E_J a^2 [\nabla\theta(x_i)]^2$. At low temperatures, the continuum limit of Hamiltonian Eq. (1) reads

$$\begin{aligned} H_{\mathrm{JJA}} = {} & \frac{1}{2}\int dx dx' \; \delta\rho(x)\, v(x - x', 0)\, \delta\rho(x') \\ & + \frac{1}{2} E_J a \int dx \; \left(\nabla\theta(x)\right)^2. \end{aligned} \tag{2}$$

Here the 1D superfluid interacts via the *bare* Coulomb potential, which we define for convenience as

$$v(\mathbf{r}, z) = \frac{e^2}{\epsilon_{\mathrm{r}}} \frac{1}{\sqrt{r^2 + z^2 + a^2}}, \tag{3}$$

where $r = |\mathbf{r}|$ and z are, respectively, the distance in the xy-plane and along the azimuthal direction between two point-charges (cf. Fig. 1). Here the lattice parameter a acts as the short-distance regularization of the interaction and ϵ_{r} is the permitivity of the insulating medium surrounding the islands. Note that in Eq. (2) we do not assume an *a priori* short-ranged, screened interaction as is usually done when dealing with JJAs.[24] This will result as a natural consequence of the interaction with the 2DEG (see below). One problem of this field-theoretical approach is that Mott-instabilities (crucial when the superfluid density is commensurate with the lattice) are lost in Eq. (2) after taking the continuum limit. One way to cure this problem is to introduce a phenomenological term $H_1 = -\int dx \; V_l(x)\, \rho(x)$, where the effective superfluid density $\rho(x)$ [cf. Eq. (10)] couples to the phenomenological potential $V_l(x)$, having the same periodicity of the lattice.[29]

The electrons in the 2DEG are described by the Hamiltonian

$$\begin{aligned} H_{\mathrm{2D}} = {} & \int d^2\mathbf{r} \; \sum_{\sigma} \left[-\frac{1}{2m} \eta_\sigma^\dagger \nabla^2 \eta_\sigma + V_{\mathrm{imp}} \eta_\sigma^\dagger \eta_\sigma \right] + \\ & + \frac{1}{2}\int d^2\mathbf{r} d^2\mathbf{r}' \; \delta\rho_{\mathrm{2D}}(\mathbf{r})\, v(\mathbf{r} - \mathbf{r}', 0)\, \delta\rho_{\mathrm{2D}}(\mathbf{r}'), \end{aligned} \tag{4}$$

where the fermionic field-operator $\eta_\sigma^\dagger \equiv \eta_\sigma^\dagger(\mathbf{r})$ creates an electron in the 2DEG with spin projection σ at spatial position $\mathbf{r} \equiv (x, y)$, and $V_{\mathrm{imp}} \equiv V_{\mathrm{imp}}(\mathbf{r})$ represents a weak static impurity potential which provides a finite resitivity and dissipation in the metal. In terms of $\eta_{\sigma}^{\dagger}(\mathbf{r}), \eta_{\sigma}(\mathbf{r})$, the density-operator $\rho_{\mathrm{2D}}(\mathbf{r})$ in the 2DEG writes $\rho_{\mathrm{2D}}(\mathbf{r}) \equiv \sum_{\sigma} \eta_{\sigma}^{\dagger}(\mathbf{r})\, \eta_{\sigma}(\mathbf{r})$, and $\delta\rho_{\mathrm{2D}}(\mathbf{r}) \equiv \rho_{\mathrm{2D}}(\mathbf{r}) - \rho_{0,\mathrm{2D}}$, with $\rho_{0,\mathrm{2D}}$ the average density in the metal.

Finally, the interaction between the 1DJJA and the 2DEG placed at a distance d (cf. Fig. 1) is described by the Hamiltonian

$$H_{\mathrm{int}} = \int d^2\mathbf{r}dx'\ \delta\rho(x')\, v(x' - \mathbf{r}, d)\, \delta\rho_{\mathrm{2D}}(\mathbf{r}). \tag{5}$$

Our goal in this Section is to derive an effective model for the 1DJJA capacitively coupled to the 2DEG. To that end we introduce the partition function of the system[33]

$$Z = \int \mathcal{D}[\rho, \theta]\, \mathcal{D}[\bar{\eta}, \eta]\ e^{-S},$$

where S is the Euclidean action of the problem

$$S = S_{\mathrm{JJA}} + S_{\mathrm{2D}} + S_{\mathrm{int}}, \tag{6}$$

where

$$\begin{aligned} S_{\mathrm{JJA}} &= \int_0^{\beta} d\tau \int dx\ i\partial_{\tau}\theta(x,\tau)\, \rho(x,\tau) + \int_0^{\beta} d\tau\ H_{\mathrm{JJA}}(\tau), \\ S_{\mathrm{2D}} &= \int_0^{\beta} d\tau \left[\int d^2\mathbf{r}\ \bar{\eta}(\mathbf{r},\tau)\,(\partial_{\tau} - \mu_{\mathrm{2D}})\,\eta(\mathbf{r},\tau) + H_{\mathrm{2D}}(\tau)\right], \\ S_{\mathrm{int}} &= \int_0^{\beta} d\tau\ H_{\mathrm{int}}(\tau). \end{aligned}$$

Here $\mu_{\mathrm{2D}} = k_{\mathrm{F}}^2/2m - eV_g$ is the effective chemical potential in the metal, with $k_{\mathrm{F}} = |\mathbf{k}_{\mathrm{F}}|$ the Fermi wavevector, and V_g the gate voltage applied to the 2DEG, which allows to change the value of $\rho_{0,\mathrm{2D}}$, and therefore, the sheet-resistance $R_{\square}$.

The first step in the derivation of an effective model for the array is to integrate out the fermionic degrees of freedom $\bar{\eta}(\mathbf{r},\tau), \eta(\mathbf{r},\tau)$ in the 2DEG. Assuming that the term S_{int} can be treated perturbatively (we check the consistency of this assumption later), the integration of the fermionic degrees of freedom in the metal yields

$$\begin{aligned} S_{\mathrm{eff}} \simeq S_{\mathrm{JJA}} - \frac{1}{2}\int d\tau d\tau' \int dx dx'\ \delta\rho(x,\tau) \\ \times v_{\mathrm{scr}}(x - x', \tau - \tau')\, \delta\rho(x',\tau'). \end{aligned} \tag{7}$$

We do not provide the details of this derivation here, and we refer the interested reader to Refs. 25 and 26. In Eq. (7) we have introduced the 1D effective screening potential $v_{\mathrm{scr}}(x - x', \tau - \tau')$, which encodes all the screening effects provided by the 2DEG. This quantity writes more conveniently in Fourier representation as[25]

$$v_{\mathrm{scr}}(k, \omega_m) \equiv \frac{1}{L_{\perp}} \sum_{k_{\perp}} \frac{[v_{\mathrm{2D}}(\mathbf{k}, d)]^2\, \chi_{0,\mathrm{2D}}(\mathbf{k}, \omega_m)}{1 + v_{\mathrm{2D}}(\mathbf{k}, 0)\, \chi_{0,\mathrm{2D}}(\mathbf{k}, \omega_m)}, \tag{8}$$

where $\omega_m = 2\pi m/\beta$ are the bosonic Matsubara frequencies,[34] and $\mathbf{k} = (k, k_{\perp})$ is the wavevector in 2D, where we have made explicit the component $k_{\perp}$ in the 2DEG, perpendicular to the 1DJJA. The quantity $v_{\mathrm{2D}}(\mathbf{k}, d) = \left(2\pi e^2/\epsilon_{\mathrm{r}}\right) \exp\left(-|\mathbf{k}|\sqrt{d^2 + a^2}\right)/|\mathbf{k}|$ is the 2D Fourier transform of the Coulomb potential Eq. (3). We assume that the length of the array is $L < \xi_{\mathrm{loc}}$, with ξ_{loc} the Anderson localization length in the 2DEG, a condition well fulfilled in practice. In that case, the density-density response function in the 2DEG, averaged over disorder configurations, writes $\chi_{0,\mathrm{2D}}(\mathbf{k}, \omega_m) = 2\mathcal{N}_{2D}^{0} D\mathbf{k}^2/\left(D\mathbf{k}^2 + |\omega_m|\right)$, where D and $\mathcal{N}_{2D}^{0}$ are, respectively, the diffusion constant and the density of states (at the Fermi energy) per spin projection.[35]

We can now define the total effective retarded interaction

$$v_{\mathrm{eff}}(k, \omega_m) = v_{\mathrm{1D}}(k, 0) - v_{\mathrm{scr}}(k, \omega_m), \tag{9}$$

where $v_{\mathrm{1D}}(k, 0) = 2e^2 K_0(|k|\, a)/\epsilon_{\mathrm{r}}$ is the Fourier transform of Eq. (3) in 1D, and $K_0(x)$ is the zeroth-order modified Bessel function.[36] Physically, the effective potential $v_{\mathrm{eff}}(k, \omega_m)$ describes the interaction among charges in the array, both via the instantaneous interaction $v_{\mathrm{1D}}(k, 0)$ arising from the direct intrawire Coulomb interaction, as well as indirectly via the coupling to the diffusive modes in the 2DEG, which corresponds to the retarded interaction $v_{\mathrm{scr}}(k, \omega_m)$ Eq. (8).

We now introduce a more convenient representation of the superfluid density in the 1DJJA. To motivate our approach, we first note that in the absence of Josephson coupling [i.e., $E_J = 0$ in Eq. (1)], the Cooper-pair occupation number n_i is a good quantum number in each island, fixed by $\bar{n}$ via the application of an external gate-voltage. Increasing E_J will evidently introduce fluctuations in n_i due to the transfer of Cooper-pairs between neighboring islands, and n_i is no longer a good quantum number. However, we expect that in the experimentally interesting regime $E_J/E_0 \sim 1$, where E_0 is the characteristic charging energy in the island, fluctuations $\Delta n_i \equiv n_i - \bar{n}$ will be of order $\Delta n_i \simeq \pm 1$, and that all other charging states such that $|\Delta n_i| \gg 1$ will be energetically forbiden. We therefore truncate those states from our description and focus on charge-fluctuations of $\Delta n_i = \pm 1$. In terms of a continuous field $\phi(x)$, which is slowly varying on the scale of a, the superfluid density in this effective model can be more conveniently written as[37]

$$\rho(x) = \left[\rho_0 - \frac{1}{\pi}\nabla\phi(x)\right] \sum_{p} e^{i2p(\pi\rho_0 x - \phi(x))}, \tag{10}$$

where the parameter ρ_0 is defined as $\rho_0 \equiv 1/a$ in the commensurate case. Note that ρ_0 is an effective parameter of our model, and cannot be interpreted as the total physical density, in contrast to truly 1D systems.[29] Only the *fluctuations* $\delta\rho\left(x\right)\equiv\rho\left(x\right)-\rho_0$ have a physical meaning in our model.

In order to obey the phase-number commutation relations in the BCS-groundstate,[32] note that the field $\phi\left(x\right)$ must verify the new commutation relation

$$\left[\theta\left(x\right),\nabla\phi\left(x'\right)\right]=i\pi\delta\left(x-x'\right). \tag{11}$$

The contribution in squared brackets in Eq. (10) describe long-wavelength density fluctuations around the average value ρ_0, while in the last term, each contribution describes low-energy density fluctuations of momentum $k\sim 2p\rho_0$, where p is an integer. When replaced into the effective action Eq. (7) we obtain the following effective model

$$S_{\text{eff}}\left[\phi\right]=S_0\left[\phi\right]+S_1\left[\phi\right]+S_2\left[\phi\right], \tag{12}$$

where the contribution S_0 corresponds to a Luttinger liquid model[29]

$$S_0\left[\phi\right]=\frac{1}{2\pi\beta L}\sum_{k,\omega_m}\left[\frac{\omega_m^2}{uK}+\frac{uk^2}{K}+\frac{\eta\left|\omega_m\right|\left|k\right|}{2\pi c}\right]\left|\phi\left(k,\omega_m\right)\right|^2. \tag{13}$$

resulting from the slow fluctuations of the density $\delta\rho\left(x\right)\sim-\nabla\phi\left(x\right)/\pi$ and from the hydrodynamic (i.e., $\left\{k,\omega_m\right\}\to 0$) sector of $v_{\text{eff}}\left(k,\omega_m\right)$. u and K are respectively the velocity of the 1D plasmon and the interaction Luttinger parameter

$$K\equiv\pi\sqrt{\frac{E_J}{E_0}}, \tag{14}$$

$$u\equiv a\sqrt{E_JE_0}, \tag{15}$$

where $E_0\equiv e^2/2C_0$ is the charging energy with respect to the ground, with $C_0=\epsilon_{\text{r}}a/4\ln\left(2d/a\right)$ the effective ground capacitance of the Josephson junction. In our treatment, due to the screening provided by the 2DEG, the static effective potential $v_{\text{eff}}\left(k,0\right)$ is effectively short-ranged for distances $x\gg d$, and therefore the Luttinger parameter K is a constant.[2949]In terms of the capacitance matrix C_{ij} of the 1DJJA, this amounts to neglecting the interjunction capacitance C, since this contribution, although relevant for density fluctuations of momentum $k\sim a^{-1}$, drops off in the long-wavelength sector $k\to 0$ (i.e. the interaction is screened in a length $L_{\text{scr}}\sim a\sqrt{C/C_0}$).[2] In the present context, the Luttinger parameter K physically represents the competition between coherence and charging effects in the array [cf. Eq. (14)]. Therefore, a large parameter K favors superconducting correlations, while a small value of K tends to destroy superconductivity due to strong charging effects.[2]

The dissipative parameter η is defined as

$$\eta\equiv\frac{c}{\epsilon_{\text{r}}8\pi}\frac{R_\square}{R_Q}, \tag{16}$$

where $R_\square$ is the sheet-resistance of the 2D film and c is a numerical constant of order $c\sim\mathcal{O}\left(1\right)$. Eq. (13) with a non-vanishing η describes a 1D plasmon-mode with a finite lifetime $\Gamma\sim\left|k\right|/\eta$.[25] Physically, a broadening of the 1D plasma mode occurs due to coupling to the diffusive modes in the 2DEG. The term $\sim\eta\left|\omega_m\right|\left|k\right|$ in Eq. (13) is the result of combining the leading contribution in powers of $\left|\omega_m\right|/Dk_{\text{TF}}\left|k\right|$ (with k_{TF} the Thomas-Fermi momentum in the 2DEG) in the expansion of the retarded potential $v_{\text{eff}}\left(k,\omega_m\right)$, and the long-wavelength fluctuations of the density $\sim\left(\nabla\phi\right)^2$, which contributes a term $\sim k^2\left|\phi\left(k,\omega_m\right)\right|^2$ in Fourier representation. Note that since the scaling dimension of the term $\sim\left|k\right|\left|\omega_m\right|$ is 2, the critical properties of the system are not modified. Moreover, for a metallic plane [cf. Ref. 10] with $R_\square\sim 0.1R_Q$, $\eta\simeq 10^{-2}\ll 1$ and it can be effectively ignored, allowing us to write

$$S_0\left[\phi\right]\simeq\frac{1}{2\pi\beta L}\sum_{k,\omega_m}\left[\frac{1}{uK}\omega_m^2+\frac{u}{K}k^2\right]\left|\phi\left(k,\omega_m\right)\right|^2. \tag{17}$$

This assumption greatly simplifies the analysis, since the action S_0 recovers Lorentz-invariance in space-time.

The next term S_1 in Eq. (12) originates in the phenomenological potential $V_l\left(x\right)$, which has the same periodicity of the array. Therefore, it can be decomposed in Fourier components as $V_l\left(x\right)=\sum_n V_n\cos\left(Qnx\right)$, with $Q=2\pi/a$. In general, all terms other than $p=n=0$ in Eq. (10) are rapidly oscillating and vanish under the integral sign. However, if $Qn=2\pi p\rho_0$, or equivalently $\rho_0a=n/p$ (i.e., the average density of bosons is commensurate with the lattice), then the term $\sim\int dx\ V_l\left(x\right)\rho\left(x\right)$ yields a term $e^{-i\left(Qn-2\pi p\rho_0\right)x}=1$ which is not oscillating and, in addition to the term $p=n=0$, we have the additional term

$$S_1\left[\phi\right]=-\frac{\lambda}{a\tau_0}\int dxd\tau\ \cos\left(2\phi\left(x,\tau\right)\right), \tag{18}$$

where we have only kept the most important commensurability ($p=1$), and where we have defined the dimensionless parameter λ

$$\lambda\equiv V_1\tau_0. \tag{19}$$

and the short-time cutoff $\tau_0\equiv a/u$. The term V_0 can be reabsorbed in a redefinition of the chemical potential of the externally imposed charge $\bar{n}$, so in the following we will not consider it. Physically, the dimensionless parameter λ is related to the QPS rate in the Josephson junction by $\Gamma_{\text{QPS}}=\lambda/\tau_0$. Estimated experimental values for Γ_{QPS} are in the order of ~ 1 GHz[21], which yields $\lambda\simeq 0.06$.

The final term in Eq. (12) comes from the dissipative part of $v_{\text{scr}}\left(k,\omega_m\right)$. Due to the strongly oscillating factors $\sim e^{-i2\pi p\rho_0x}$ in Eq. (10), it results in the local dissipative term

$$S_2\left[\phi\right]=-\frac{\eta}{a}\int dxd\tau d\tau'\sum_{p>0}\frac{1}{p}\frac{\cos 2p\left[\phi\left(x,\tau\right)-\phi\left(x,\tau'\right)\right]}{\left(\tau-\tau'\right)^2}, \tag{20}$$

This contribution is consistent with that of Ref. 26, obtained in the context of Luttinger liquids capacitively coupled to diffusive metals. In spite of the small magnitude of η, we will show that this contribution has important consequences for the critical properties of the 1DJJA, in contrast to the term proportional to η in Eq. (13).

In the following we study the critical properties and phases of the model obtained in Eq. (12).

III. PHASE DIAGRAM

A. Weak-coupling renormalization group analysis

We first focus on the phases of the 1DJJA at $T = 0$. To that end, we perform a weak-coupling renormalization group (RG) analysis of the model Eq. (12), assuming that S_1 and S_2 in Eqs. (18) and (20) respectively are weak perturbations to the Luttinger liquid S_0 in Eq. (17). Since the action S_0 is Lorentz-invariant in space and imaginary time, we adopt an RG procedure that rescales homogenously space and time. As usual, we assumme that the original theory is defined up to a certain momentum cutoff $\Lambda(l) = \Lambda_0 e^{-l}$ (with $\Lambda_0 \sim a^{-1}$), and we study how the action S_0 is renormalized upon integration of high-energy modes in a window between $\Lambda(l)/s < |\mathbf{q}| < \Lambda(l)$, with $s = e^{dl}$, where we have employed the compact notation $\mathbf{q} \equiv \left\{k, -\frac{\omega_m}{u}\right\}$ and $\mathbf{x} \equiv \{x, u\tau\}$.

We obtain the perturbative RG-flow equations of the model by performing a one-loop correction in S_2 and a two-loop correction in S_1, and requiring that the term S_0 is invariant upon scaling.[38] We obtain the RG-flow equations

$$\frac{dK(l)}{dl} = \left[-2\pi\eta(l) - (2\pi)^2 K(l)\lambda^2(l)C\right]K^2(l), \quad (21)$$

$$\frac{du(l)}{dl} = -2\pi\eta(l)u(l)K(l), \quad (22)$$

$$\frac{d\lambda(l)}{dl} = [2 - K(l)]\lambda(l), \quad (23)$$

$$\frac{d\eta(l)}{dl} = [1 - 2K(l)]\eta(l), \quad (24)$$

where the numerical constant C is of order unity.

Note that both S_1 and S_2 tend to destroy superconducting correlations in the Luttinger liquid phase, a fact that is reflected in Eq. (21) where the Luttinger parameter $K(l)$ is renormalized to *smaller* values, meaning that charging effects are enhanced. This can be interpreted as an effective increase of the charging energy E_0 in Eq. (14). In addition, since S_2 is the only term that breaks the Lorentz invariance of the theory, note that the plasmon velocity $u(l)$ is proportional only to $\eta(l)$, and is independent of $\lambda(l)$.

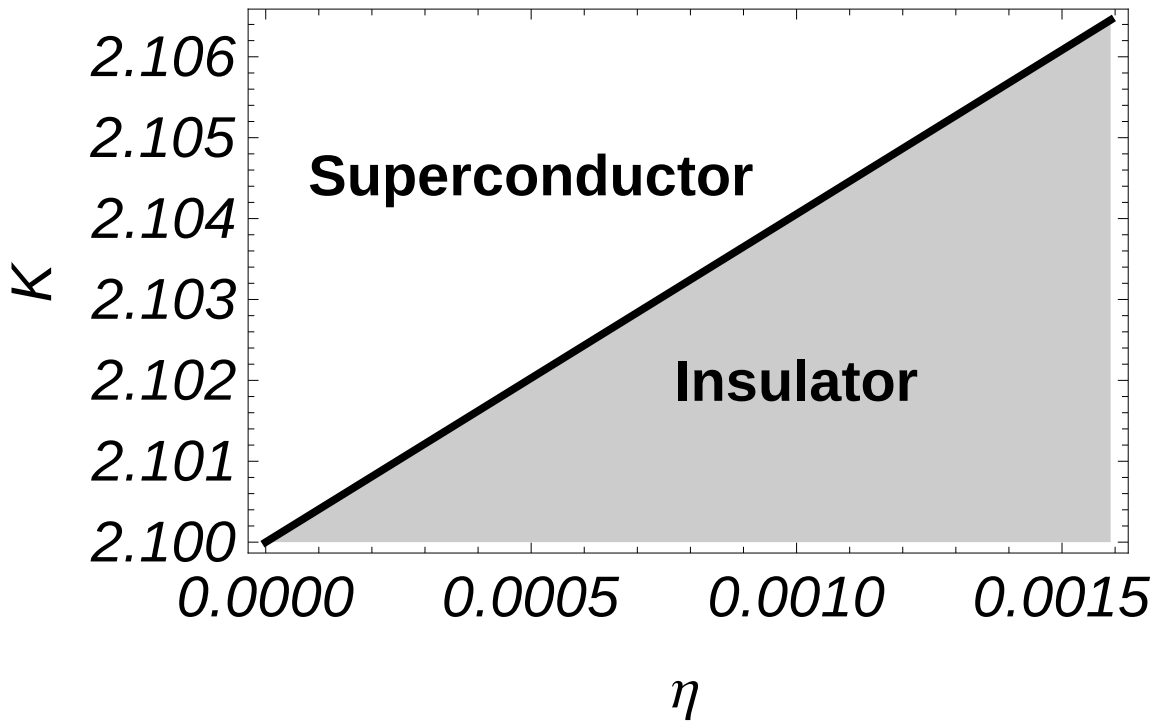

Figure 2: Schematic phase diagram of the 1DJJA in the $K-\eta$ plane, obtained from the integration of the RG-flow Eqs. (21)-(24), with the initial parameter $\lambda_0 \equiv \lambda(l=0) = 0.01$. An increase of $R_\square$ in the 2DEG, and consequently, of the dissipative parameter η, can induce a SIT. Note that, in absence of dissipation, the critical value $K_c = K_c(\lambda_0) \simeq 2.1$ is slightly shifted with respect to the value $K_c(\lambda_0 \to 0) \to 2$.

When $K(l) < 2$, the perturbative parameter $\lambda(l)$ flows to strong-coupling [cf. Eq. (23)], and the perturbative RG procedure is no longer valid. In the limit $\eta \to 0$ we recover the usual Mott-transition of the BKT-type described by the sine-Gordon model, and below the critical value $K_c = 2$, the 1DJJA is in the insulating phase.[2,29,39,40] Using Eq. (14), this means that in absence of dissipation, the SIT occurs for $E_J/E_0 = (2/\pi)^2$.[2] Note that our situation corresponds strictly to the case when the superfluid density in the 1DJJA is commensurate to the lattice, and is in clear distinction to the non-commensurate situation (i.e., $\lambda = 0$), where dissipation (i.e., the term S_2) becomes relevant for $K(l) < 1/2$, inducing a different kind of non-superconducting groundstate.[26]

In the present case, the scaling dimension of the dissipative parameter $\eta(l)$ is always smaller than that of $\lambda(l)$, which means that for $K(l) \simeq 2$, S_1 is a stronger perturbation as compared to S_2. Therefore, one would expect the nature of the non-superconducting groundstate to be determined essentially by S_1. However, based on this fact, one could naively conclude that the term S_2 is unimportant near the SIT, a conclusion we prove incorrect. In fact, a more detailed analysis reveals the importance of the term S_2 near the SIT. Physically, the coupling to the diffusive degrees of freedom in the 2DEG quenches charge-fluctuations in the 1DJJA, resulting in an enhanced effective charging energy E_0^*. This phenomenon is more precisely described by the RG-flow equation for $K(l)$ [cf. Eq. (21)], where $K(l)$ is renormalized to *lower* values by $\eta(l)$. Indeed, near the SIT, a small increase in the initial value $\eta_0 \equiv \eta(l=0)$ (i.e., an increase in $R_\square$) can effectively control the RG-flow of $K(l)$ and therefore, that of $\lambda(l)$, inducing the SIT. We illustrate this point in Fig 2, where the schematic phase diagram obtained by integration of the RG-flow Eqs. (21)-(24), with initial parameter $\lambda_0 \equiv \lambda(l=0) = 0.01$. Note the stabilization of the insulating groundstate due to Ohmic dissipation induced by the coupling to the 2DEG.

In a first approximation, this effect is similar to the dissipation-driven SIT observed in 2DJJAs capacitively coupled to a diffusive 2DEG.[10,24,41] However, important differences appear with respect to the 2D case. In that case, it was argued that dissipation produced a renormalization of the effective parameters E_J and E_C of the array due to the incomplete screening of the Coulomb interaction in a certain frequency-regime.[24] Physically, the slow diffusive response of the 2DEG cannot follow the faster dynamics of the 2D plasma mode, and cannot screen it efficiently. However, in the 1D geometry the 1D plasmon is effectively very well screened by the 2DEG[25], and it could be naively concluded that no dissipation-driven SIT should be observed. However, this screening effect is compensated by the presence of strong backscattering occuring in 1D [i.e., action S_2, Eq. (20)], and originated in the retarded interaction $v_{\mathrm{eff}}(x,\tau)$. The net result is that the dissipation-driven SIT is restored in 1D.

Although one expects the nature of the non-superconducting groundstate to be of the Mott-insulating type, by analogy with the well-known results for the sine-Gordon model[2,29,39,40], strictly speaking we cannot extrapolate the results in this Section to the strong-coupling situation, and a different method is needed in that regime.

B. Self-consistent harmonic approximation

To gain more insight into the phase in which the parameter $\lambda(l)$ flows to strong-coupling, in this Section we make use of the variational self-consistent harmonic approximation[42]. This method consist in finding the optimal propagator $g^{-1}_{\mathrm{tr}}(\mathbf{q})$ of a Gaussian trial action of the 1DJJA

$$S_{\mathrm{tr}} = \frac{1}{2\beta L}\sum_{\mathbf{q}} g^{-1}_{\mathrm{tr}}(\mathbf{q})\left|\phi_{\mathbf{q}}\right|^2, \tag{25}$$

where $\phi_{\mathbf{q}}$ is the Fourier transform of $\phi(x,\tau)$. Here we have introduced the compact notation $\mathbf{q} = (k, -\omega_m/u)$. The idea is to minimize the variational free-energy

$$F_{\mathrm{var}} \equiv F_{\mathrm{tr}} + \frac{1}{\beta}\left\langle S_{\mathrm{eff}} - S_{\mathrm{tr}}\right\rangle_{\mathrm{tr}}, \tag{26}$$

where the "trial" free-energy F_{tr} is

$$F_{\mathrm{tr}} = -\frac{1}{2\beta}\sum_{\mathbf{q}} \log\left[\beta L g_{\mathrm{tr}}(\mathbf{q})\right] \tag{27}$$

The factor 1/2 in Eqs. (25) and (27) come from the constraint $\phi^*(\mathbf{q}) = \phi(-\mathbf{q})$ since $\phi(x,\tau)$ is a real field, a fact that reduces the number of independent degrees of freedom .

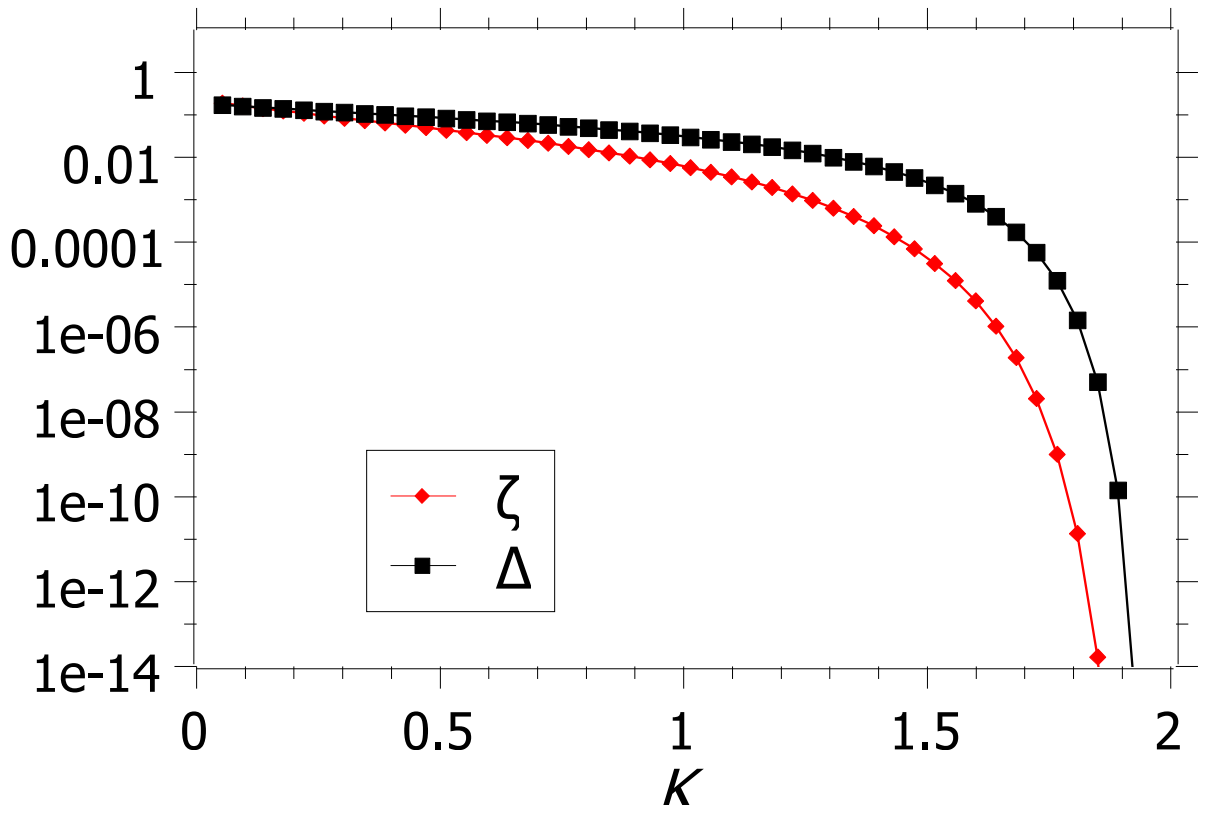

Figure 3: Dimensionless SCHA parameters Δ and ζ as a function of K, calculated for the parameters $\eta = 0.01$, $\lambda = 0.05$. We obtain non-vanishing values only in the region $K \lesssim 2$ (note the abrupt increase in that region), consistent with the results of the RG-analysis.

The minimization of F_{var} in Eq. (26) with respect to $g_{\mathrm{tr}}(\mathbf{q})$ yields the self-consistent equation for $g_{\mathrm{tr}}(\mathbf{q})$

$$\begin{aligned} g^{-1}_{\mathrm{tr}}(\mathbf{q}) &= \frac{1}{\pi u K}\omega_m^2 + \frac{u}{\pi K}k^2 + \frac{4\lambda}{a\tau_0}e^{-\frac{2}{\beta L}\sum_{\mathbf{q}'} g_{\mathrm{tr}}(\mathbf{q}')} \\ &- \frac{8\eta}{a}\int_0^\beta d\tau\, \frac{\cos(\omega_m\tau) - 1}{\tau^2}\times \\ &\times e^{-4\frac{1}{\beta L}\sum_{\mathbf{q}'}\left[1-\cos(\omega'_m\tau)\right]g_{\mathrm{tr}}(\mathbf{q}')}. \end{aligned} \tag{28}$$

In general, the solution of this equation has to be found numerically. However, for small λ and η the analytical solution

$$g^{-1}_{\mathrm{tr}}(\mathbf{q}) = g^{-1}_{LL}(\mathbf{q}) + \frac{\zeta}{a}\left|\omega_m\right| + \frac{\Delta}{a\tau_0}, \tag{29}$$

is obtained. Here $g^{-1}_{LL}(\mathbf{q}) = \frac{1}{\pi u K}\omega_m^2 + \frac{u}{\pi K}k^2$ is the Luttinger liquid propagator, corresponding to the action Eq. (13) (for $\eta = 0$). Physically, this propagator describes an insulator (given by a non-vanishing gap or "mass" term Δ) with Ohmic-dissipative dynamics (encoded in a non-vanishing ζ). Note that dissipation dominantes for frequencies $|\omega_m| > \Delta/\zeta\tau_0$. These parameters are found solving the following set of non-linear equations

$$\zeta = 8\pi\eta\left(\frac{\zeta K\pi + 2\sqrt{K\pi\Delta}}{4}\right)^{2K}, \tag{30}$$

$$\Delta = 4\lambda\left(\frac{\zeta K\pi + 2\sqrt{K\pi\Delta}}{4}\right)^{K}, \tag{31}$$

obtained replacing the solution Eq. (29) back into Eq. (28). Starting from the self-consistent solution of Eqs. (30) and (31) for Δ in absence of dissipation (i.e. $\eta = 0$), we can study the regime $\eta \ll \lambda \ll 1$ perturbatively in η, and we obtain the following estimate for the gap increase due to dissipative effects

$$\delta\Delta \simeq 2\pi^2 \frac{\eta K \Delta_0^2}{\lambda}. \tag{32}$$

This result is consistent with the fact that dissipation in the density (i.e., field ϕ) quenches charge-fluctuations and therefore favors an insulating groundstate.

In Fig. 3 we show numerical results for Δ and ζ as a function of K for the values $\lambda = 0.05$ and $\eta = 0.01$. Note the sharp increase of both Δ and ζ for $K < 2$. This result is consistent with the RG-analysis, which predict the breakdown of the Luttinger liquid phase for $K < 2$ in the weak-coupling regime. Within the SCHA, the physics of the strong-coupling fixed point is encoded in non-vanishing values of ζ and Δ, providing a complementary description to the RG-analysis.

IV. TRANSPORT PROPERTIES

In this section we concentrate on the dc-conductivity of the 1DJJA, a quantity of central interest in experiments.[1,2] We first focus on the current-density $j(x)$. Since the field $\nabla\theta(x)/\pi$ is the momentum of Cooper-pairs [cf. Eq. (2)], the usual minimal coupling procedure $\nabla\theta(x)/\pi \to [\nabla\theta(x) - 2eA(x)]/\pi$ (with e the electron charge and A the vector potential) in Hamiltonian Eq. (2) allows to obtain the current as $j(x) \equiv -\delta H_{JJA}/\delta A(x)$. In our problem, it explicitly reads[29]

$$j(x) = uK\left(\frac{2e}{\pi}\right)\left[\nabla\theta(x) - 2eA(x)\right]. \tag{33}$$

The conductivity along the wire is obtained from the Kubo formula[29,34]

$$\sigma(\omega) \equiv \frac{\chi_{jj}^R(0,\omega)}{i(\omega + i\delta)}, \tag{34}$$

where $\chi_{jj}^R(k,\omega) \equiv \lim_{i\omega_m \to \omega + i\delta} \chi_{jj}(\mathbf{q})$ is the retarded current-current correlation function and $\chi_{jj}(\mathbf{q}) \equiv \langle j^*(\mathbf{q})\, j(\mathbf{q})\rangle = \delta^2 \ln Z/\delta A(\mathbf{q})\,\delta A^*(\mathbf{q})\big|_{A=0}$ is the current-current correlation function obtained in the linear-response regime. It is convenient to express this correlator as $\chi_{jj}(\mathbf{q}) = \chi_{jj}^d + \chi_{jj}^p(\mathbf{q})$, where $\chi_{jj}^d \equiv -(2e)^2 uK/\pi$ is the diamagnetic contribution and

$$\chi_{jj}^p(\mathbf{q}) \equiv \left(\frac{2e}{\pi}\right)^2 (uK)^2 k^2 \langle\theta(\mathbf{q})\,\theta(-\mathbf{q})\rangle, \tag{35}$$

is the paramagnetic term.[34] In absence of current-decaying mechanisms [i.e., $\lambda = \eta = 0$ in Eq. (6)], the conductivity writes

$$\sigma_0(\omega) = \frac{(2e)^2}{\hbar} uK\left[\delta(\omega) + i\mathrm{P}\left(\frac{1}{\pi\omega}\right)\right],$$

where we have restored the Planck constant and where we have used that $\chi_{jj}^p(\mathbf{q}) \to 0$ in the limit $k = 0$.[29] Note that the real part of $\sigma_0(\omega)$ consists of a Drude-peak at $\omega = 0$, as expected for a superconductor. This result can be understood from the fact that the total charge current $J_e = \int dx\; j(x)$ is a conserved quantity in absence of QPS and dissipation processes, i.e., it commutes with the hamiltonian H_{JJA}.

The effect of a finite η in the Gaussian sector of the theory [cf. Eq. (13)] has been studied in Ref. 25, and produces a broadening of the plasmon peak, whose width Γ vanishes as $\Gamma \sim |k|$. Consequently, only taking into account this effect, a well-defined Drude-peak in $\sigma(\omega)$ for $\omega = 0$ is recovered, and the system should behave as a perfect conductor.

Let us now study the effects of the terms S_1 and S_2. When λ and η are irrelevant perturbations (in the RG sense), their effects on the conductivity can be studied within the theoretical framework of the memory function formalism.[43] In this approach, the central assumption is that the Kubo formula for the conductivity Eq. (34) can be recasted as[29]

$$\sigma(\omega, T) = \frac{i(2e)^2}{\pi\hbar} \frac{uK}{\omega + M(\omega, T)}, \tag{36}$$

where $M(\omega, T)$ (i.e., the memory function) is a meromorphic function depending on the terms in the Hamiltonian responsible for degrading the current, and hence producing a finite resistivity. Current-decay originated in QPS and in the coupling to the dissipative modes in the 2DEG induce finite resistivity in the 1DJJA for all temperatures $T < T_c$. In particular for temperatures $T \ll T_c$, and perturbatively in λ and η, we obtain

$$\varrho(T) = \frac{\hbar}{a(2e)^2}\left[A_1 T^{2K-3} + A_2 T^{2K}\right] \tag{37}$$

where

$$A_1 \equiv \lambda^2 4\pi^3 \left[\cos\left(\frac{\pi K}{2}\right) B\left(\frac{K}{2}, 1 - K\right)\right]^2 \left(\frac{2\pi a}{u}\right)^{2K-3}, \tag{38}$$

$$A_2 \equiv \eta 32\pi^3 \cos\left[(1+K)\pi\right] B\left[1+K, -1-2K\right] \left(\frac{2\pi a}{u}\right)^{2K}, \tag{39}$$

where the function $B(x,y)$ is defined as $B(x,y) \equiv \Gamma(x)\,\Gamma(y)/\Gamma(x+y)$, and $\Gamma(x)$ is the standard Euler's Gamma function.[36] The term $\sim T^{2K-3}$ in Eq. (37) is the contribution due to QPS processes, consistent with former theoretical predictions.[18,44] The second term $\sim T^{2K}$ originates in backscattering effects induced by dissipation, and is consistent with the behavior predicted by Cazalilla *et al.*[26] This last effect can be interpreted as a frictional drag produced by the diffusive modes in the 2DEG.[45] Note that at lowest order in λ and η, the two contributions add up independently, indicating that for temperatures $T^* < T \ll T_c$, where $T^* \equiv \sqrt[3]{A_1/A_2}/2\pi\tau_0$, the resistivity in the 1DJJA is dominated by frictional drag, while for $T < T^* \ll T_c$ the effect of QPS takes over.

The non-trivial effects due to the renormalization of the bare couplings can be taken into account integrating the RG-flow Eqs. (21)-(24), and injecting them in the above Eqs. (37), (38) and (39). We integrate the RG-flow up to the scale given by the temperature $a(l) = a(0)\, e^l = u(l)/2\pi T$, and we use formula Eq. (37) with the parameters of the model calculated at the scale $a(l)$. This allows to obtain $\varrho(T(l))$ vs $T(l)$.

In Fig. 4 we show the resistivity $\varrho(T)$ of the 1DJJA, calculated for different values of the parameter K and using the estimations for the bare parameters $\lambda_0 = 0.01$ and $\eta_0 = 0.01$. The results are normalized to a “high-temperature” resistivity $\varrho(T_0)$, where $T_0 \simeq a(0)/u = \tau_0$, represents a high-temperature cutoff in the theory (e.g., T_c).

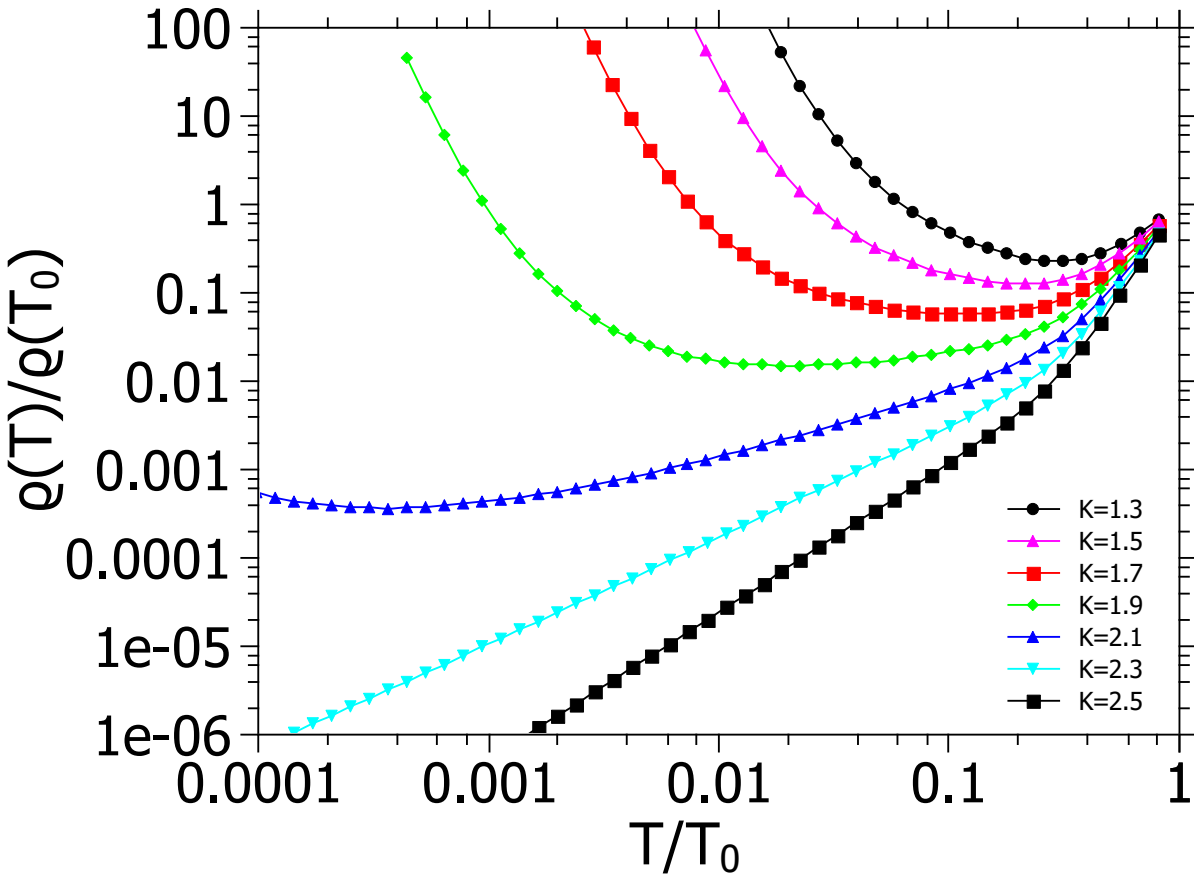

Figure 4: Dc-resistivity $\varrho(T)$ of the 1DJJA, normalized to a “high-temperature” value $\varrho(T_0)$, as a function of T/T_0, calculated for the parameters $\lambda_0 = 0.01$ and $\eta_0 = 0.01$, and for different values of $K = \pi\sqrt{E_J/E_0}$. A low-temperature upturn of $\varrho(T)$ signals the formation of the insulating phase.

Note that for the values $K = 2.5$ and $K = 2.3$, the resistivity shows a monotonically decreasing behavior, indicating a superconducting groundstate and consistent with the RG-analysis of Sec. III A. We also note a small kink around $T^* \sim 0.4\, T_0$, signalling the aforementioned crossover from dissipation-dominated to QPS-dominated resistivity. For $K = 2.1$, the resistivity first decreases and then shows a low-temperature upturn, indicating that the array is near the quantum critical point K_c. Finally, for lower values of K, the insulating behavior in the 1DJJA is clear. Since both the integration of the RG-flow equations and the calculation of the memory-function formulas are perturbative in λ and η, the calculation of the resistivity must be stopped whenever $\lambda(l)$ or $\eta(l)$ become of order unity.

In Fig. 5, we show the resistivity as a function of T/T_0, calculated for fixed $K = 2.3$ and $\lambda = 0.01$, and for different values of parameter η. We see that for $\eta = 0$ (i.e., $R_\square = 0$ in the 2DEG), the array shows superconducting behavior, and the resistivity due to QPS processes is well described by the predicted power-law $\varrho(T) \sim T^{2\tilde{K}-3}$, with $\tilde{K} = K(l \to \infty) \simeq 2.2$ the renormalized value predicted by Eq. (23). Upon increasing the parameter η, the resistivity of the array increases, developing the aforementioned kink, but most importantly, the low-temperature resistivity develops an upturn, indicating a dissipation-driven phase transition to the insulating phase.

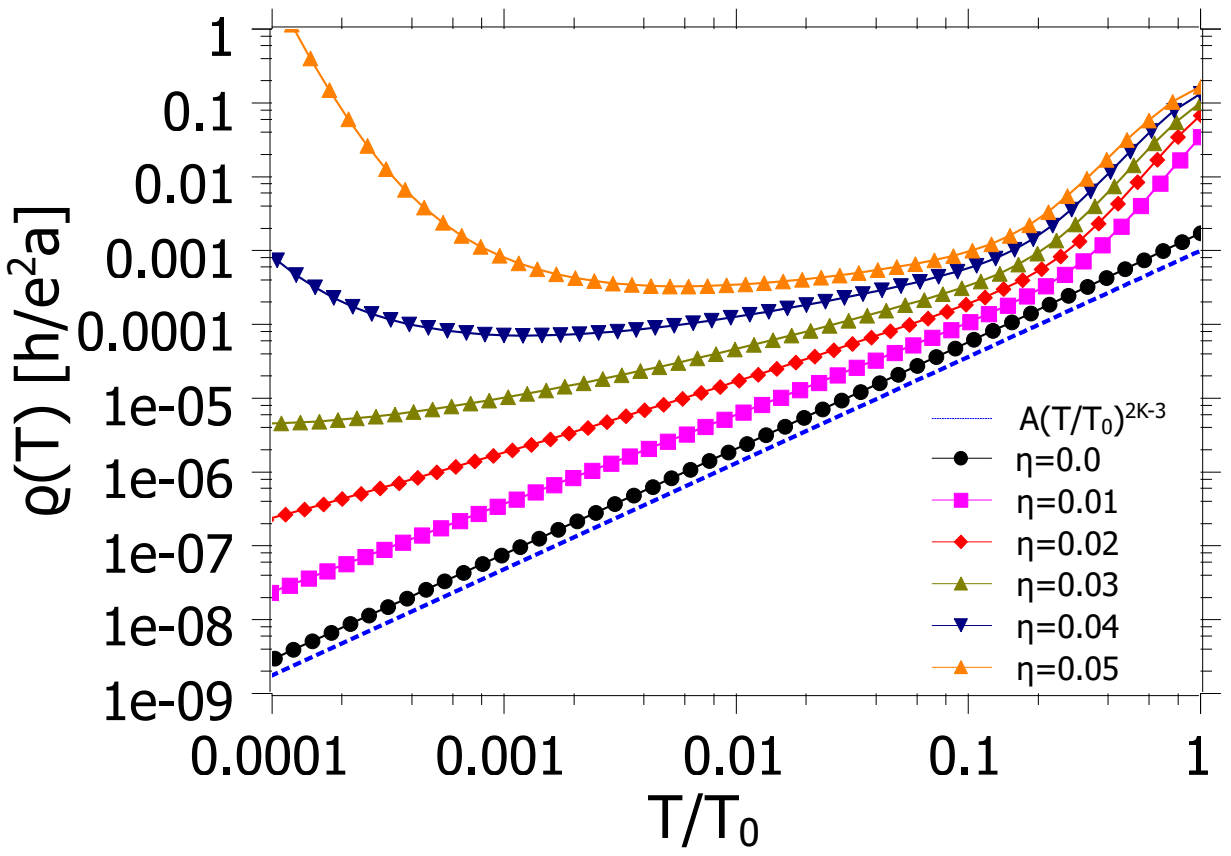

Figure 5: Resistivity of the 1DJJA (in units of h/e^2a) as a function of T/T_0, calculated for parameters $K = 2.3$ and $\lambda = 0.01$ and for different values of η. Although in absence of dissipation, the array is in the superconducting phase, a dissipation-driven SIT occurs upon increasing η, consistent with the results in Fig. 2. The curve $\varrho(T) \sim T^{2K-3}$ is shown for comparison.

More insight into the insulating phase can be obtained using the Luther-Emery refermionization solution for $K = 1$.[29,46] In absence of dissipation (i.e., $\eta = 0$) an exact solution is obtained in terms of non-interacting fermions, with a gap $\tilde{\Delta} \equiv \pi a \lambda$ in their spectrum of excitations. Using the Kubo formula, one obtains the following expression for the dc-conductivity at low temperatures $T \ll \tilde{\Delta}$

$$\sigma(\omega) \approx \frac{e^2}{\hbar} u \sqrt{\frac{2\pi T}{\tilde{\Delta}}} e^{-\tilde{\Delta}/T} \delta(\omega) .$$

This contribution arises from the excited quasiparticles above the gap $\tilde{\Delta}$, which have an exponential population at low enough temperatures. This infinite conductivity occurs because in absence of dissipation, excited quasiparticles are infinitely long-lived. Using the memory-function approach for the refermionized problem in the regime $\eta \ll \lambda, T \ll \tilde{\Delta}$, we find the analytical result

$$\sigma\left(\omega=0\right)=\frac{e^{2}}{\hbar}\frac{c_{2}}{\eta}\frac{1}{\tau_{0}^{2}\tilde{\Delta}^{2}}\frac{\tilde{\Delta}}{T}e^{-\tilde{\Delta}/T},$$

where c_2 is a numerical coefficient $c_2 \simeq \mathcal{O}(1)$. As expected, dissipation introduced a finite lifetime in the quasiparticles, and a finite resistivity is obtained at $\omega = 0$.

V. SUMMARY AND CONCLUSIONS

We have investigated the properties of a linear JJA capacitively coupled to a diffusive 2DEG placed in close proximity. Using a bosonization approach, we have derived an effective model for the 1DJJA, and have obtained its critical properties and phases at $T = 0$. Our main result is the possibility to observe a SIT tuned by the parameter $\eta \sim R_\square/R_Q$ [cf. Eq. (16)]. This setup could be used to investigate the superconductor-insulator transition in a 1DJJA under better controlled experimental conditions as compared to other setups used in the past.[12–15] Our work could shed some light on the understanding of other 1D superconducting systems showing a similar behavior, such as ultra-thin superconducting wires built by molecular templating[6,8,47] or by e-beam lithography[48] techniques.

We have shown that besides the more or less trivial static screening effect, the presence of a 2DEG induces dissipative effects in the quantum dynamics of the 1DJJA due to backscattering processes induced by the dynamically screened Coulomb interaction, and explicitly depend on the sheet-resistance $R_\square$ of the 2DEG. These dynamical effects play an important role in the quantum phase diagram of the 1DJJA. This situation is different from previous approaches in higher dimensions.[24,41] Indeed, in 1D the plasmon mode is almost statically screened[25], and this would lead to the naive conclusion that dynamical effects are not important. However, a more careful analysis shows that backscattering originated in the dynamically screened Coulomb potential has the effect of restoring the SIT. In our system, these dynamical effects have important consequences for the critical properties of the array, and should be possible to observe them in dc-transport measurements. Physically, the coupling to diffusive modes in the metal induces charging effects which are local in space (i.e., of the order of the lattice parameter a of the 1DJJA) but which are non-local in time (i.e., Ohmic dissipation effects), and tend to quench charge fluctuations, rendering superconductivity weaker.

By the means of a weak-coupling RG-analysis and a variational approach, we predict a SIT driven by the presence of dissipation in the 2DEG. This SIT is of the BKT-type and mediated by unbinding of QPS/anti QPS pairs, like in the dissipationless case.[39] Near the critical line the effects of QPS are stronger than those originated in dissipation and results in a SIT. This scenario is corroborated by a subsequent variational analysis of action Eq. (12), which suggests the formation of a gap Δ in the spectrum of excitations of the 1DJJA [cf. Eq. (29)].

Our results suggest that dissipation renormalizes the QPS-rate to *higher* values and the ratio $\sqrt{E_J/E_0}$ to *lower* values [cf. Eqs. (21)-(24)], rendering superconductivity in the 1DJJA weaker. Eventually, an increase of $R_\square$ [and therefore of η, in view of Eq. (16)], could drive the system into the insulating phase, as can be seen in Figs. 2 and 5. This phenomenon is different to the case studied by Cazalilla *et al.*, where QPS processes were absent, and it was dissipation *itself* that drove the quantum phase transition for the critical value $K_c = 1/2$.[26]

We have also studied the consequences on the temperature-dependent dc-resistivity of the array $\varrho\left(T\right)$. We have shown that a non-vanishing $R_\square$ induces a rich behavior of $\varrho\left(T\right)$. In particular in the superconducting phase, where the 1DJJA is in the Luttinger liquid universality class, and the effects of QPS and dissipation are perturbative, the resistivity of the array $\varrho\left(T\right)$ follows a power-law behavior $\varrho\left(T\right) = A_1 T^{\nu_1} + A_2 T^{\nu_2}$, with exponents $\nu_1 = 2K - 3$ and $\nu_2 = 2K$ [cf. Eq. (37)] generated by QPS and dissipation, respectively. Therefore, the results of this paper could be relevant in the interpretation of experimental results of transport through superconducting circuits subject to dissipative effects. In the insulating phase, the low-temperature dc-resistivity is expected to show thermally-activated behavior.[2,29] In particular for $K = 1$, the resulting model can be studied analytically with a refermionization approach, and results in a resistivity $\varrho\left(T\right) \sim \eta T e^{\Delta/T}/\Delta$. Quite importantly, note in this expression that the resistivity depends also implicitly on η via a renormalization of the gap η.

Acknowledgments

We acknowledge useful discussions with I. Pop, W. Guichard and F. Hekking. This work was supported by the Swiss National Foundation under MaNEP and division II.

---

[1] G. Schön and A. D. Zaikin, Physics Reports **198**, 237 (1990), ISSN 0370-1573.

[2] R. Fazio and H. van der Zant, Physics Reports **355**, 235 (2001).

[3] D. B. Haviland, Y. Liu, and A. M. Goldman, Phys. Rev. Lett. **62**, 2180 (1989).

[4] N. Mason and A. Kapitulnik, Phys. Rev. Lett. **82**, 5341 (1999).

[5] N. Mason and A. Kapitulnik, Phys. Rev. B **65**, 220505 (2002).

[6] A. Bezryadin, C. N. Lau, and M. Tinkham, Nature **404**, 971 (2000).

[7] K. Y. Arutyunov, D. S. Golubev, and A. D. Zaikin, Phys. Rep. **464**, 1 (2008).

[8] A. Bezryadin, J. Phys.: Condens. Matter **20**, 043202 (2008).

[9] H. S. J. van der Zant, W. J. Elion, L. J. Geerligs, and J. E. Mooij, Phys. Rev. B **54**, 10081 (1996).

[10] A. J. Rimberg, T. R. Ho, Ç. Kurdak, J. Clarke, K. L. Campman, and A. C. Gossard, Phys. Rev. Lett. **78**, 2632 (1997).

[11] Y. Takahide, R. Yagi, A. Kanda, Y. Ootuka, and S.-i. Kobayashi, Phys. Rev. Lett. **85**, 1974 (2000).

[12] E. Chow, P. Delsing, and D. B. Haviland, Phys. Rev. Lett. **81**, 204 (1998).

[13] W. Kuo and C. D. Chen, Phys. Rev. Lett. **87**, 186804 (2001).

[14] H. Miyazaki, Y. Takahide, A. Kanda, and Y. Ootuka, Phys. Rev. Lett. **89**, 197001 (2002).

[15] Y. Takahide, H. Miyazaki, and Y. Ootuka, Phys. Rev. B **73**, 224503 (2006).

[16] M. P. A. Fisher, P. B. Weichman, G. Grinstein, and D. S. Fisher, Phys. Rev. B **40**, 546 (1989).

[17] M. P. A. Fisher, Phys. Rev. Lett. **65**, 923 (1990).

[18] A. D. Zaikin, D. S. Golubev, A. van Otterlo, and G. T. Zimányi, Phys. Rev. Lett. **78**, 1552 (1997).

[19] J. E. Mooij and C. J. P. M. Harmans, New Journal of Physics **7**, 219 (2005).

[20] I. M. Pop, I. Protopopov, F. Lecocq, Z. Peng, B. Pannetier, O. Buisson, and W. Guichard, Nature Physics **6**, 589 (2010).

[21] V. E. Manucharyan, N. A. Masluk, A. Kamal, J. Koch, L. I. Glazman, and M. H. Devoret, cond-mat/1012.1928 (2010).

[22] N. Giordano, Physica B **203**, 460 (1994).

[23] A. O. Caldeira and A. J. Leggett, Phys. Rev. Lett. **46**, 211 (1981).

[24] K.-H. Wagenblast, A. van Otterlo, G. Schön, and G. T. Zimányi, Phys. Rev. Lett. **79**, 2730 (1997).

[25] A. M. Lobos and T. Giamarchi, Phys. Rev. B **82**, 104517 (2010).

[26] M. A. Cazalilla, F. Sols, and F. Guinea, Phys. Rev. Lett. **97**, 076401 (2006).

[27] P. Goswami and S. Chakravarty, Phys. Rev. B **73**, 094516 (2006).

[28] G. Refael, E. Demler, Y. Oreg, and D. S. Fisher, Phys. Rev. B **75**, 014522 (2007).

[29] T. Giamarchi, *Quantum Physics in One Dimension* (Oxford University Press, Oxford, 2004).

[30] V. L. Berezinskii, Sov. Phys. JETP **32**, 493 (1971).

[31] J. M. Kosterlitz and D. J. D J Thouless, J. Phys. C: Solid State Phys. **6**, 1181 (1973).

[32] M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, 1996), 2nd ed.

[33] J. Negele and H. Orland, *Quantum Many Particle systems*, Frontiers in Physics (Addison-Wesley, Reading, Mass., 1987).

[34] G. D. Mahan, *Many-Particle Physics*, Physics of Solids and Liquids (Kluwer Academic/Plenum Publishers, New York, 2000), 3rd ed.

[35] E. Akkermans and G. Montambaux, *Mesoscopic Physics of Electrons and Photons* (Cambridge University Press, Cambridge, 2007).

[36] M. Abramowitz and I. Stegun, *Handbook of mathematical functions* (Dover, New York, 1972).

[37] F. D. M. Haldane, Phys. Rev. Lett. **47**, 1840 (1981).

[38] R. Shankar, Rev. Mod. Phys. **66**, 129 (1994).

[39] R. M. Bradley and S. Doniach, Phys. Rev. B **30**, 1138 (1984).

[40] L. I. Glazman and A. I. Larkin, Phys. Rev. Lett. **79**, 3736 (1997).

[41] A. Vishwanath, J. E. Moore, and T. Senthil, Phys. Rev. B **69**, 054507 (2004).

[42] R. P. Feynman, *Statistical Mechanics* (Benjamin, Reading, MA, 1972).

[43] W. Götze and P. Wölfle, Phys. Rev. B **6**, 1226 (1972).

[44] T. Giamarchi, Phys. Rev. B **46**, 342 (1992).

[45] A. G. Rojo, J. Phys.: Condens. Matter **11**, R31 (1999).

[46] A. Luther and V. J. Emery, Phys. Rev. Lett. **33**, 589 (1974).

[47] C. N. Lau, N. Markovic, M. Bockrath, A. Bezryadin, and M. Tinkham, Phys. Rev. Lett. **87**, 217003 (2001).

[48] Y. Chen, S. D. Snyder, and A. M. Goldman, Phys. Rev. Lett. **103**, 127002 (2009).

[49] Indeed, in the static limit $\omega_m = 0$, the effective screening potential writes $v_{\mathrm{scr}}(k,0) = 2e^2 K_0(2kd)/\epsilon_{\mathrm{r}}$ and in the limit $kd \to 0$ compensates the logarithmic divergence of $v_{\mathrm{1D}}(k,0)$ [cf. Eq. (9)], and yields $\lim_{k\to 0} v_{\mathrm{eff}}(k,0) = 2e^2 \ln(2d/a)/\epsilon_{\mathrm{r}}$.[25]